

Speed limit of the insulator–metal transition in magnetite

S. de Jong^{1†}, R. Kukreja^{1,2†}, C. Trabant^{3,4,5}, N. Pontius⁴, C. F. Chang^{3,6}, T. Kachel⁴, M. Beye⁴, F. Sorgenfrei^{4,7}, C. H. Back^{1,8}, B. Bräuer¹, W. F. Schlotter⁹, J. J. Turner⁹, O. Krupin^{9,10}, M. Doehler³, D. Zhu¹, M. A. Hossain¹, A. O. Scherz^{1,10}, D. Fausti^{11,12}, F. Novelli¹², M. Esposito^{11,12}, W. S. Lee¹, Y. D. Chuang¹³, D. H. Lu¹⁴, R. G. Moore¹, M. Yi¹, M. Trigo¹, P. Kirchmann¹, L. Pathey¹⁵, M. S. Golden^{1,16}, M. Buchholz³, P. Metcalf¹⁷, F. Parmigiani^{11,12}, W. Wurth⁷, A. Föhlisch^{4,5}, C. Schüßler-Langeheine^{3,4*} and H. A. Dürr^{1*}

As the oldest known magnetic material, magnetite (Fe₃O₄) has fascinated mankind for millennia. As the first oxide in which a relationship between electrical conductivity and fluctuating/localized electronic order was shown¹, magnetite represents a model system for understanding correlated oxides in general. Nevertheless, the exact mechanism of the insulator–metal, or Verwey, transition has long remained inaccessible^{2–8}. Recently, three-Fe-site lattice distortions called trimerons were identified as the characteristic building blocks of the low-temperature insulating electronically ordered phase⁹. Here we investigate the Verwey transition with pump–probe X-ray diffraction and optical reflectivity techniques, and show how trimerons become mobile across the insulator–metal transition. We find this to be a two-step process. After an initial 300 fs destruction of individual trimerons, phase separation occurs on a 1.5 ± 0.2 ps timescale to yield residual insulating and metallic regions. This work establishes the speed limit for switching in future oxide electronics¹⁰.

When crossing the Verwey transition of magnetite ($T_V = 123$ K) from above, charge fluctuations marking the conducting state freeze into an electronically ordered structure with octahedrally coordinated Fe²⁺ and Fe³⁺ sites, resulting in a hundred-fold increase in the resistivity¹. This transition is accompanied by a change in the crystal symmetry from a high-temperature cubic inverse spinel to a monoclinic phase, the fine details of which have eluded crystallographers for decades. An important step was taken recently, demonstrating that the low-temperature structure consists of a network of three-Fe-site distortions dubbed trimerons, encompassing two outer 3+ and a central 2+ octahedral Fe_B site ion⁹. In addition, the t_{2g} orbitals within a trimeron are ordered,

meaning that the trimeron lattice (Fig. 1) is the true microscopic face of the electronic order in magnetite. Fluctuations to this trimeron order have been observed up to 80 K above T_V in neutron scattering studies^{11,12}.

In many oxide materials^{13,14} the insulator–metal transition has been discussed in terms of freezing-in fluctuating lattice and electronic (charge, spin and orbital) order, sometimes in combination with the occurrence of phase separation^{15,16}. However, owing to the many competing degrees of freedom, the close energetic proximity of the different phases often obscures the exact nature of these phase transitions as they are probed in thermal equilibrium¹⁷. In magnetite, the Verwey transition does not involve changes in the spin ordering, allowing a focus purely on the role of the lattice and electronic ordering. As such, magnetite serves as a model system to understand the mechanism behind the insulator–metal transition for a large group of materials.

Here we show how the insulator–metal transition in magnetite can be unravelled in the time domain. We use time-resolved X-ray diffraction¹⁸ and optical reflectivity^{19,20} to disentangle the lattice and electronic degrees of freedom and study the role of phase separation in the Verwey transition. Starting from the insulating phase at 80 K, energy is rapidly injected into the electronic system through femtosecond laser excitation. The lattice and electronic order responses are probed using soft X-ray diffraction at the linac coherent light source²¹ (LCLS; see Methods and Fig. 1). We show that the insulator–metal transition proceeds in two distinctly different stages. An ultrafast (<300 fs) punching of holes into the quasi-static trimeron lattice is the first step, followed by a 1.5 ± 0.2 ps rearrangement of residual trimerons. In the following, we will characterize these two steps by first monitoring the lattice

¹Stanford Institute for Energy and Materials Sciences, SLAC National Accelerator Laboratory, 2575 Sand Hill Road, Menlo Park, California 94025, USA,

²Stanford University, Department of Materials Science and Engineering, California 94305, USA, ³Universität zu Köln, II. Physikalisches Institut, Zülpicher Straße 77, 50937 Köln, Germany, ⁴Helmholtz-Zentrum Berlin für Materialien und Energie, Albert-Einstein-Str. 15, 12489 Berlin, Germany, ⁵Universität

Potsdam, Institut für Physik und Astronomie, Karl-Liebknecht-Strasse 24-25, 14476 Potsdam, Germany, ⁶Max Planck Institut für Chemische Physik fester

Stoffe (MPI CPFS), Nöthnitzer Str. 40, 01187 Dresden, Germany, ⁷Universität Hamburg, Department of Physics and Center for Free-Electron Laser Science,

Luruper Chaussee 149, 22761 Hamburg, Germany, ⁸Universität Regensburg, Physikalisches Institut, Universitätsstrasse 31, 93053 Regensburg, Germany,

⁹Linac Coherent Light Source, SLAC National Accelerator Laboratory, 2575 Sand Hill Road, Menlo Park, California 94025, USA, ¹⁰European XFEL GmbH,

Albert-Einstein-Ring 19, 22761 Hamburg, Germany, ¹¹Department of Physics, University of Trieste, 34127 Trieste, Italy, ¹²Eletra-Sincrotrone Trieste SCnA,

Basovizza I-34012, Italy, ¹³Advanced Light Source, LBNL, 1 Cyclotron Rd, Berkeley, California 94720, USA, ¹⁴Stanford Synchrotron Radiation Lightsource,

SLAC National Accelerator Laboratory, 2575 Sand Hill Road, Menlo Park, California 94025, USA, ¹⁵SwissFEL, Paul Scherrer Institut, 5232 Villigen PSI,

Switzerland, ¹⁶Van der Waals-Zeeman Institute, University of Amsterdam, Science Park 904, 1098 XH Amsterdam, The Netherlands, ¹⁷Purdue University,

School of Materials Engineering, West Lafayette, Indiana 47907, USA. †These authors contributed equally to this work.

*e-mail: christian.schuessler@helmholtz-berlin.de; hdurr@slac.stanford.edu

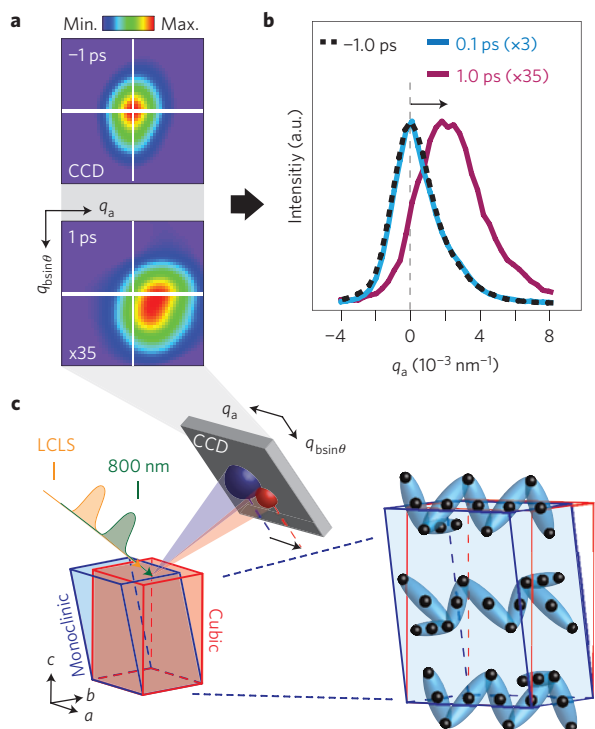


Figure 1 | Experimental optical pump-X-ray probe set-up and response of the soft X-ray diffraction intensity from the monoclinic reflections of the low-temperature phase of Fe_3O_4 on optical pumping. **a**, CCD detector images of the (001/2) electronic order recorded at the Fe L_3 -edge before and after pumping with 4.9 mJ cm^{-2} . The pump-induced shift of the diffraction peak shows a clear in-plane component along q_a . We note that the orthogonal direction is a superposition of in-plane (q_a) and out-of-plane (q_c) directions. **b**, Horizontal line scans of the (001/2) peak at $q_b = 0$ before 0 fs, at 0.1 ps and at 1 ps pump-probe delay time. **c**, Sketch of the experimental set-up. The magnetite crystal is shown as the blue (red) block in the monoclinic (cubic) structure. Inset: low-temperature unit cell with the electronically ordered trimeron lattice represented using blue ellipsoids after ref. 9.

and electronic order parameters (diffraction intensity) succeeded by discussion of the electronic order coherence length. The latter, together with time-resolved optical reflectivity, reveals a picosecond phase segregation into insulating domains of residual electronic order and a percolative network of coexisting domains supporting polaronic charge transport.

The low-temperature monoclinic structure is established through freezing-in of various phonon modes across T_V (ref. 9). Some of these frozen phonons (most notably the X_1 and Δ_5 modes²²) act as primary order parameters for the insulating trimeron phase. This gives rise to low-temperature Bragg peaks that are forbidden in the cubic high-temperature phase (Supplementary Information). Here we monitor the low-temperature lattice order through (001) and (110) Bragg diffraction and the electronic order through the (001/2) Bragg peak, visible when the X-ray energy is tuned to the electronic $2p$ - $3d$ core-valence resonance of the B-site Fe atoms (see methods and Supplementary Information).

Figure 2a shows the temporal evolution of the lattice order by means of the scattering intensity for the (001) Bragg peak for three different pump fluences. The pump pulse triggers electronic excitations within the trimeron lattice, resulting in the creation of trimeron holes in the network. This expresses itself as the ultrafast drop in scattering intensity (denoted A, orange arrow). This ultrafast response of a subset of atomic displacements attests to the strong coupling between electronic and lattice degrees

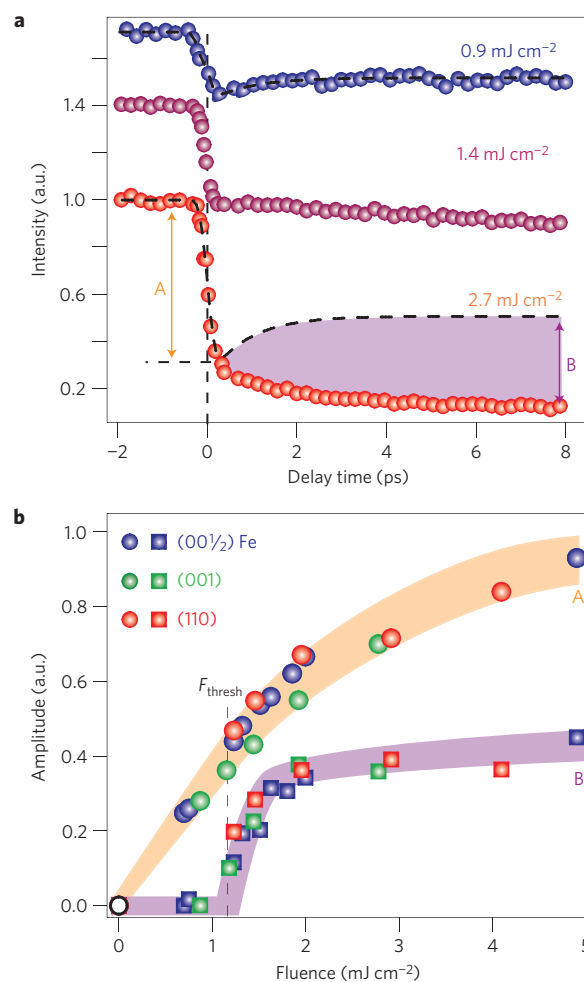


Figure 2 | Differing femtosecond and picosecond responses for the decay of the trimeron-related X-ray diffraction intensity. **a**, Normalized (001) diffraction intensity versus time delay for pump fluence values as indicated (traces offset). The dashed line fits extract the characteristic timescales for pump fluences below $1.3 \pm 0.1 \text{ mJ cm}^{-2}$. The orange arrow indicates a strong quench (A) of the diffraction from the ordered trimeron lattice in the first 300 fs. For longer times and pump fluences above $1.3 \pm 0.1 \text{ mJ cm}^{-2}$ the signal from the remnant trimeron lattice decays monotonically (B process defined as the difference between high- and extrapolated low-fluence behaviours, purple shading). **b**, Pump fluence dependence of the fast ($t < 300 \text{ fs}$) intensity drop A (orange shading) and the slower intensity decay B (purple shading) of the diffraction intensity from the magnetite trimeron lattice from time traces such as those shown in **a**. The fast quench (A) is present for all fluences. The slower B decay appears only above a threshold pump fluence $F_{\text{thresh}} = 1.3 \pm 0.1 \text{ mJ cm}^{-2}$. This threshold shifts to higher pump fluences with decreasing initial sample temperatures (Supplementary Information).

of freedom in the system. After the initial, ultrafast intensity drop seen for all fluences, a further picosecond evolution takes place. Its nature depends on the pump fluence. At low fluence, a thermally equilibrated trimeron lattice reasserts itself after about 1 ps, leading to an increase in scattering intensity (top curve in Fig. 2a). We note that the initial low-temperature state is re-established only after microseconds owing to the low thermal conductivity¹⁸ of the system. For higher fluence (lowest curve in Fig. 2a), the picosecond behaviour is different. It exhibits a monotonously continuing reduction in diffraction intensity with increasing pump-probe delay time (parameter B, purple shading). Figure 2b shows the resulting decomposition of the time profiles

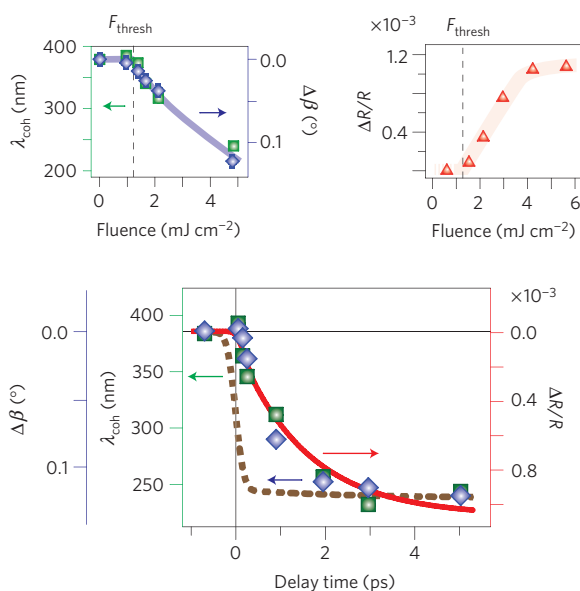


Figure 3 | Fast trimeron lattice quench followed by a picosecond transformational process. Bottom: the figure compares X-ray data (blue/green symbols and dashed brown line) taken at the (001/2) reflection (Fe L_3 -edge) and optical reflectivity (red line, representing an exponential fit to the data in the Supplementary Information). The trimeron-order coherence length is derived as $\lambda_{\text{coh}} = 2\pi/\text{FWHM}$ with FWHM being the full-width at half-maximum of the diffraction data shown in Fig. 1b. Statistical errors in determining λ_{coh} and the change in monoclinic tilt angle, $\Delta\beta$, are given by the respective symbol sizes. The reductions in λ_{coh} and $\Delta\beta$ occur concomitant with the increase of $\Delta R/R$ with a time constant of 1.5 ± 0.2 ps, as shown by the red line (Supplementary Fig. S3). This decay occurs with a delayed onset as clearly indicated by the unchanged λ_{coh} and $\Delta\beta$ values at 200 fs time delay (Fig. 1b) and reflects the structural modifications towards the cubic lattice where metallic charge fluctuations reduce the coherence of the remnant patches of electronic order. As a comparison: the trimeron lattice diffraction intensity versus time (dashed brown solid line in arbitrary units centred at 0 fs time delay) shows a fast quench reflecting the time resolution of the experiment. The X-ray data were taken with a pump fluence of 4.9 mJ cm^{-2} . Left inset: fluence-dependent λ_{coh} and $\Delta\beta$ data taken at a fixed delay time of 5 ps. The data show a threshold fluence, $F_{\text{thres}} = 1.3 \pm 0.1 \text{ mJ cm}^{-2}$, above which the diffraction peaks exhibit a change of the monoclinic angle $\Delta\beta$ (0.23° would correspond to the cubic case). The diffraction peaks also broaden, linked to a reduction of the coherence length of the trimeron lattice remnants, λ_{coh} , by up to 40%. Right inset: fluence-dependent $\Delta R/R$ data taken at a fixed delay time of 5 ps, probing the onset of the metallic phase above $1.3 \pm 0.1 \text{ mJ cm}^{-2}$ (Supplementary Information).

into the two parameters, A and B, as a function of pump fluence. The figure also demonstrates that the behaviour of the (110) lattice Bragg peak is identical to that of the (001) one. As the next step, we add the analysis of time traces from the (001/2) electronic order diffraction intensity^{23–25} into Fig. 2b. It is immediately evident that all of the data can be collapsed onto a single, universal plot. The continued picosecond decay B exhibits a clear threshold pump fluence of $1.3 \pm 0.1 \text{ mJ cm}^{-2}$. The threshold value is a surprisingly good match to the energy required to drive magnetite from 80 K across the Verwey transition in thermodynamic equilibrium (Supplementary Information).

Up to this point, we have shown that optical excitation launches a strongly coupled charge–lattice motion, locally destroying the trimeron order. Now we address the question of whether this process can instigate metallic behaviour. By probing the coherence length of the electronically ordered phase after the optical

excitation, we show that the system segregates into coexisting metallic and insulating domains on a 1.5 ± 0.2 ps timescale. In Fig. 3 we show the evolution of the coherence length, λ_{coh} , extracted from the diffraction peak width and the change in the monoclinic tilt angle, $\Delta\beta$. Figure 1 shows that a $\Delta\beta$ change results in a characteristic shift of the diffraction peak (Supplementary Information). The relative diffraction intensity (dashed brown line in Fig. 3) is strongly suppressed within 300 fs of the optical excitation pulse. The intensity goes on to reach values below 5% of the static value on the picosecond timescale. In contrast to the fast intensity quench, the changes of $\Delta\beta$ and λ_{coh} exhibit a very different characteristic timescale of 1.5 ± 0.2 ps for this pump fluence. Moreover, $\Delta\beta$ and λ_{coh} changes are observed only later than 200 fs (the earliest data point following optical excitation included in Fig. 3). This means that on the timescale of the ultrafast intensity quench, the low-temperature monoclinic lattice tilt angle and the trimeron lattice coherence length remain unchanged with respect to the static case. We note that the observed static coherence length of $\lambda_{\text{coh}} = 385 \pm 10 \text{ nm}$ is in good agreement with literature values³.

The observed shrinking correlation length of the insulating trimeron lattice indicates island formation, providing space for a coexisting, metallic phase. We used optical reflectivity to detect its existence. In thermal equilibrium, the transition from insulating to metallic behaviour is accompanied by the appearance of a spectral feature centred at 725 nm (ref. 19). We found the same feature to appear in time-resolved, pump–probe experiments with a 1.5 ± 0.2 ps time constant (Supplementary Information). The observed delayed onset and subsequent increase of metallic character (red line in Fig. 3) mirrors the decay of the insulating phase. The fluence dependence (right inset in Fig. 3) shows that the metallic phase is fully developed above 4 mJ cm^{-2} .

Therefore, on short timescales, shooting holes into the trimeron lattice weakens the network, but does not destroy its long-range order. This behaviour of negligible change in correlation length despite strong reduction in intensity has also been observed in nickelates²⁶, where it is associated with small fluctuations in amplitude and phase of charge order. In contrast, in magnetite, large phase fluctuations in the electronic order result in the observed picosecond decrease of the correlation length in Fig. 3. Thus, a transformational regime is entered on the picosecond timescale that is marked by a break-up of the trimeron lattice into patches separated by a coexisting metallic phase that scrambles the phase coherence of the surviving trimerons islands (Fig. 4). This is accompanied by a relaxation of the monoclinic lattice tilt $\Delta\beta$ in the trimeron islands towards the right-angle cubic value (see schematics in Fig. 1). After 5 ps in Fig. 3, the deviation from the cubic lattice angle is 0.11° , compared with 0.23° for the static, low-temperature case. One of the most remarkable aspects of the data of Fig. 3 is that the lattice transformation towards the cubic ideal does not happen synchronously with the ultrafast trimeron annihilation process. The transformational, picosecond regime is entered only at pump fluences above the threshold value, because both λ_{coh} and the monoclinic tilt change only above $1.3 \pm 0.1 \text{ mJ cm}^{-2}$ (left inset to Fig. 3), in agreement with the minimal fluence for metallic character seen in the optical reflectivity (right inset to Fig. 3).

Bringing together all pieces of the puzzle, as shown in Fig. 4, we can now describe, step-by-step, the energy-flow processes following femtosecond optical excitation of the electronically ordered Fe B-sites in magnetite.

On a femtosecond timescale, the optical pump pulse induces transitions in the electronic system (red arrows in Fig. 4a), leading to the creation of holes in the trimeron lattice (dashed in Fig. 4b).

This process, which represents trimeron annihilation (dashed in Fig. 4b), triggers relaxation of the monoclinic distortions related to a subset of the frozen phonon modes, namely the ones with the largest amplitude situated on the end points of the trimerons⁹

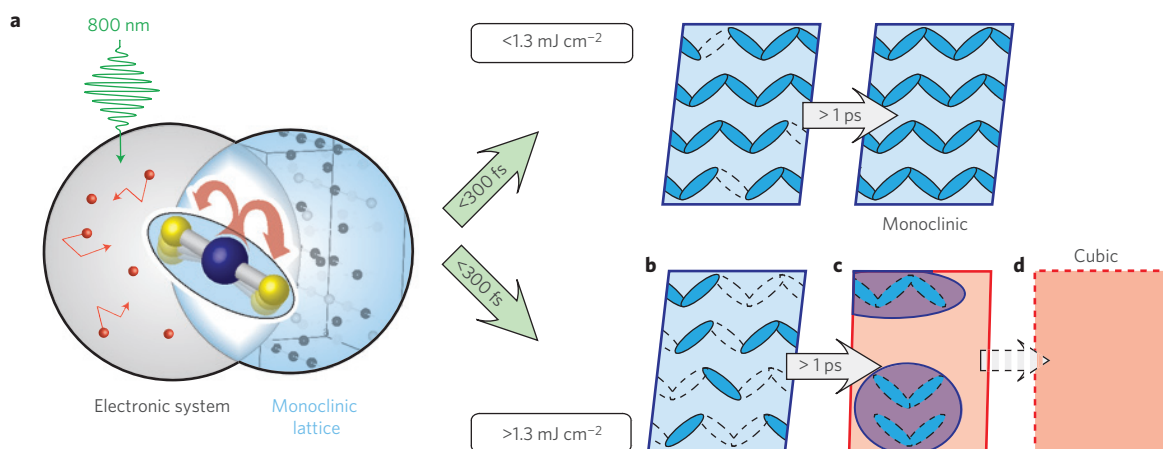


Figure 4 | Summary of the workings of the Verwey transition in non-equilibrium pump-probe form. **a**, Ultrafast trimeron annihilation due to laser excited Fe^{2+} - Fe^{3+} charge transfer launches strongly coupled electronic and lattice dynamics. **b,c**, For a pump fluence above $1.3 \pm 0.1 \text{ mJ cm}^{-2}$ trimeron holes (**b**) transform with a time constant of $1.5 \pm 0.2 \text{ ps}$ to a state with shrinking patches of remnant phase-scrambled electronic order (**c**). Its structure is approaching that of the cubic case in **d**, embedded in a network supporting mobile charge fluctuations (red) derived from the aggregation of the trimeron vacancies in **b**. **d**, The end of the line would be the fully metallic, cubic phase.

(Supplementary Information). It is these frozen X_1 and Δ_5 modes that dominate the monitored diffraction peaks (Supplementary Information). The energy of these X_1 and Δ_5 modes is between 10 and 30 meV (ref. 27), yielding characteristic vibrational timescales between 400 and 150 fs. We note that possible coherent oscillations of these modes would be smeared out as a result of the time resolution ($\sim 300 \text{ fs}$) of our experiment.

After 300 fs, the residual trimeron lattice retains the long-range order of the insulating phase (dark blue in Fig. 4b), albeit possessing excess energy that is dissipated on a longer (picosecond) timescale.

If the pump fluence is low, the trimeron lattice then recovers and the system simply returns to a warmer version of the electronically ordered insulating state, through equilibration of the hot phonon modes. The long-range coherence of all the other frozen displacement modes of the monoclinic structure is still preserved.

For a pump fluence above threshold, the excess energy is sufficient to drive the system through a point of no return. We note that the dynamics of this unfreezing depends on the starting temperature before the pump: lower temperatures requiring larger pump fluences (Supplementary Fig. S2). For 80 K starting temperature, the transformational regime (Fig. 4c) is entered on a characteristic timescale of $1.5 \pm 0.2 \text{ ps}$. The observed relaxation of the monoclinic tilt indicates the melting of the Γ -mode distortions (Supplementary Information) on this timescale. The 80 K threshold fluence of $1.3 \pm 0.1 \text{ mJ cm}^{-2}$ corresponds to the absorption of about one photon per monoclinic unit cell, containing 30 trimeron sites (Supplementary Information). A single 1.5 eV photon can create about 5–10 electron–hole pairs above the bandgap^{5,19}; thus, the threshold fluence corresponds to the destruction of about 1 in 4 trimerons.

This transformational process switches the system from being a long-range ordered trimeron lattice (dark blue in Fig. 4) with holes in it (dashed), into a patchwork of modified but still electronically ordered remnants (purple in Fig. 4c), with structural parameters leaning towards those of the charge-fluctuating, conducting cubic matrix in which they reside (red, seen in optical reflectivity). This transition from the residual coherent trimeron network to a phase-segregated state has to proceed through coalescence of trimeron holes and thus involves the hopping of charges together with their associated lattice distortions between trimeron lattice sites. We note that the electronic order observed after 1.5 ps could—in principle—be a different one to that in the ground state. However, the optical data as well as the observed reduction of the monoclinic

tilt angle indicate that the 800 nm pump drives the system (partially) into the high-temperature phase. The fact that electronic order is still observed at such picosecond timescales clearly indicates the existence of insulating regions in the sample. Hence, the observed B process is the signature of polaronic transport, further eroding the ordered regions on a picosecond timescale after the optical excitation. This polaronic hopping timescale matches well with the charge density relaxation time seen in inelastic neutron scattering associated with fluctuating trimeron order above T_V (ref. 12). These observations all point to the fact that the threshold fluence, translating to trimeron lattice collapse for a volume fraction below $\sim 75\%$, is that required to create a percolative network of charge-fluctuating, metallic, sites in the trimeron matrix (Supplementary Information).

This pump-induced transformation can thus be regarded as a non-equilibrium version of the thermodynamic Verwey transition seen in the conductivity–temperature phase diagram of magnetite. Consequently, the data show how magnetite dynamically evolves towards its energy minimum during the Verwey transition: initially holes in the long-range ordered trimeron lattice allow the trimerons to become mobile and form shorter-range ordered domains surrounded by charge-fluctuating regions. The coalescence of the remaining trimerons, driven by their desire to keep the monoclinic distortion intact, is connected to the organization of hundreds of atoms involved in the frozen displacement modes of the monoclinic structure. The bulk metallic phase is reached as soon as the charge-fluctuating regions form a percolation pathway through the magnetite crystal.

In conclusion, our experiments show that insulating, electronically ordered, low-temperature magnetite exhibits phase segregation on a $1.5 \pm 0.2 \text{ ps}$ timescale following ultrafast ($< 300 \text{ fs}$) laser-induced trimeron hole creation. We identify a residual low-temperature, insulating phase embedded in a phase resembling the high-temperature metallic lattice, the latter forming a percolative charge-fluctuating path throughout the sample. The switching of conductivity in such an archetypal complex oxide at the picosecond timescale makes these systems faster than the best graphene transistors²⁸ developed so far. The understanding we have gained as to how the transformation between the two states straddling the Verwey transition takes place could aid in the choice and design of oxide materials aiming at harnessing the enormous differences in electrical conductivity available in these systems.

